





<b>CITY OF LAS VEGAS</b>	<u><b>DEPARTMENT of BUILDING and SAFETY</b></u> <b>OFFSITE INSPECTION and TESTING SECTION</b> <u><b>Materials Testing Laboratory</b></u>	<b>Procedure No.:</b>  <b>109</b>
	<b>Procedure:</b> <b>Material Qualification – Aggregate Base (with RAP)</b>	

Revision Number	Prepared By	Reviewed By	Approved By	Date Issued
<b>0</b>	<b>GGJ</b>	<b>GGJ</b>	<b>TEH</b>	<b>GGJ</b>
Date	10-18-10	11-9-10	12-3-10	12-3-10
<b>1</b>	<b>GGJ</b>	<b>GGJ</b>	<b>TEH</b>	<b>GGJ</b>
Date	3-23-11	3-24-11	3-28-11	4-1-11
<b>2</b>				
Date	1-17-12	1-24-13	1-24-13	1-24-13
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				
Date				

DEPARTMENT of BUILDING and SAFETY

OFFSITE INSPECTION and TESTING SECTION

Materials Testing Laboratory

City of Las Vegas

Material Qualification – Aggregate Base Material with Recycled Asphalt Pavement (RAP)

Procedure No. 109 Revision 2

*The italicized and underlined sections of this policy note Revision 2 changes.*

*The City of Las Vegas (CLV) is a member of the Interagency Quality Assurance Committee (IQAC). The CLV has adopted the IQAC procedure of Type 2 Aggregate Base Materials containing Recycled Asphaltic Pavement (RAP) aggregates as noted below.*



LAS VEGAS  
CITY COUNCIL

CAROLYN G. GOODMAN  
MAYOR

STAVROS S. ANTHONY  
MAYOR PRO TEM

LOIS TARKANIAN  
STEVEN D. ROSS  
RICKI Y. BARLOW  
BOB COFFIN  
BOB BEERS

ELIZABETH N. FRETWELL  
CITY MANAGER

CHRIS KNIGHT  
DIRECTOR

BUILDING & SAFETY  
333 N. RANCHO DRIVE  
LAS VEGAS, NEVADA  
89106

TDD  
702-386-9108

ADMINISTRATION  
702-229-6092

PERMITS  
702-229-6251

INSPECTIONS  
702-229-6914

OFF-SITE INSPECTIONS  
702-229-6337

CODE ENFORCEMENT  
702-229-6615

LAND DEVELOPMENT  
702-229-6371

**1.0 PURPOSE:** This procedure is to outline the current CLV policy and procedure for qualification, and Quality Assurance (QA) sampling and testing of Type 2 Aggregate Base Materials containing a blend of **70% (minimum)** virgin aggregates and **30% (maximum)** recycled asphaltic pavement (RAP) aggregates. The mean oil content shall be 1.2% with a +0.3% tolerance. The Total Oil Content of the blended material (virgin aggregate and RAP) **shall not exceed 1.5%**. Please note that final acceptance of materials will be based upon the material sampled in-place at the project site, per section 106 of the Standard Specifications.

1.1 Each individual location or "pit" shall be referred to as a "source".

1.2 The maximum qualification period is six (6) months for aggregates base materials blended with Recycled Asphalt Pavement (RAP) aggregates. The entire qualification process must be completed prior to the first day of April and the first day of October of each calendar year.

NOTE: The pit / source name shall include "RAP"

**2.0 REFERENCE CODES AND STANDARDS:**

**2.1 Clark County Uniform Standard Specification**

- 2.1.1 Section 106, "Control of Materials"
- 2.1.2 Section 208 "Trench Excavation and Backfill",
- 2.1.3 Section 302 "Aggregate Base Courses",
- 2.1.4 Section 704 "Base Aggregates"

**2.2 Other:**

- 2.2.1 NRS 338.176, NAC 625.550,

- 2.2.2 The most current ASTM, AASHTO, NDOT test procedures as indicated in the applicable sections of the Uniform Standard Specifications.

### 3.0 STATEMENT OF POLICY:

#### 3.1 SUBMITTAL

- 3.1.1 Submittal format shall be completed in accordance with the current CLV procedure and in compliance with the NRS 338.176 and NAC 625.550 statutes.
- 3.1.2 The Supplier or their representative shall submit a transmittal letter and Type 2 Materials Report to the CLV for review and approval. The *report submittal* shall be submitted and approved *by the CLV* prior to the utilization of the material. The CLV must receive the transmittal within twenty-one (21) days of the sampling.
- 3.1.3 Notification of samples not in compliance with the Standard Specifications is required; however, a report is not. Samples without notification, or a qualification submittal within the 21-day period, will be considered, by the CLV, to be outside of the Standard Specifications and require re-sampling and testing.

### 4.0 REPORT:

- 4.1 The report must be prepared by, or the direction of a Professional Engineer registered in the State of Nevada. The Report shall be on a standard form<sup>1</sup> generated by the CLV, include a graphical representation of the "Proctor" value(s), and include the pit name and location. The report must be signed and stamped by the responsible engineer.
- 4.2 Discrepancies between test results will be reviewed on a case-by-case basis. The CLV will notify the Supplier of substantial test variation within 10 days of receipt of the qualification submittal.
- 4.3 The Report shall include, at a minimum, the following information:
- 4.3.1 Sieve Analysis (*blend*)
  - 4.3.2 RAP - % Oil Content (blend)
  - 4.3.3 Liquid Limit (blend)
  - 4.3.4 Plasticity Index (blend)
  - 4.3.5 Fractured Faces (blend)
  - 4.3.6 Percentage Wear (blend)
  - 4.3.7 Resistance (R Value) (blend)
  - 4.3.8 Total Available Water Soluble Sodium Sulfate (blend)
  - 4.3.9 Proctor values with curve and rock correction (blend)
  - 4.3.10 Report stamped by the Professional Engineer of record

4.4 If testing is provided by another laboratory, that data shall be stamped by the laboratory engineer and included in the report.

**5.0 SAMPLING AND TESTING:**

5.1 Materials shall be sampled and tested as follows:

5.1.1 The Supplier or their representative shall notify CLV a minimum of 24 hours prior to obtaining the sample. Sampling must be performed during normal working hours.

5.1.2 All samples of aggregate base for Bi-Annual Qualification shall be "cut" from the "belt" of the blended material. When circumstances do not allow for sampling during production, the supplier / representative must coordinate with the CLV representative to identify an alternative plan for sampling.

5.1.3 An approved testing laboratory shall obtain a sufficient size samples for splitting and testing. A CLV representative shall be present at the time the samples are obtained and a split of the samples shall be provided to the CLV representative for testing.

5.1.4 If CLV personnel are not present during the sampling and splitting of the materials, the results of the sample will not be accepted.

5.2 The most current AASHTO, ASTM, NDOT test procedures shall be used. Testing requirements shall be from the applicable sections of the Standard Specifications.

5.3 The AASHTO Methods T180 and T224 (as applicable) shall be used for the moisture-density value.

5.4 Approval to use the material, as Type 2 Aggregate Base containing RAP, does not constitute acceptance of the material. All construction materials are subject to inspection and / or testing by the responsible agency personnel. Any material that does not conform to the engineering characteristics of those materials approved for use shall be removed and replaced with acceptable material.

**6.0 QUALITY ASSURANCE (QA) TESTING:**


6.1 The CLV will perform QA testing of the aggregate produced at that pit location. The frequency of QA testing for aggregate blended with recycled asphalt pavement (RAP) will be on a random basis or a minimum of two (2) samples per approval period.

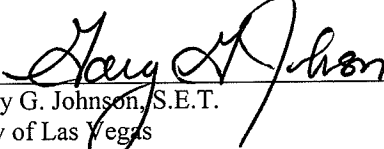
6.2 One of the samples will be the Bi-Annual sample. The remaining samples may be taken at any time during the approval period time frame at the discretion of the CLV from the pit or project location.

6.3 Should the responsible CLV find test results, which do not meet specifications, the other members of the aggregate producer shall be notified. The CLV may accommodate minor adjustments for "tuning" of an operation during normal operations. This courtesy shall not be extended during the Bi-Annual Qualification process. CLV shall determine the course of action required for these samples.

**7.0 EFFECTIVE DATE AND APPROVALS:**

EFFECTIVE DATE: February 1, 2013

  
\_\_\_\_\_  
Tom E. Hayes, P.E. 1-24-13  
City of Las Vegas Date  
Inspections Manager

  
\_\_\_\_\_  
Gary G. Johnson, S.E.T. 1-24-13  
City of Las Vegas Date  
Materials Testing Supervisor

# Attachment 1

## City of Las Vegas Standard Form for Type II Aggregate Base Containing Recycled Asphalt Pavement (RAP) Aggregate Submittal Form

Aggregate Producer Name: \_\_\_\_\_

Pit Name: \_\_\_\_\_

General Location (i.e. cross streets): \_\_\_\_\_

Date Sampled: \_\_\_\_\_

Legal Description: \_\_\_\_\_

Section: \_\_\_\_\_ Township: \_\_\_\_\_ Range: \_\_\_\_\_

Sieve Analysis			Test Name	Test Results	Specification
Sieve Size	Percent Passing (Blend)	Specification (%)	Moisture-Density Relationship		AASHTO T180
1"		100	Maximum Density(pcf)		Nearest Whole Number
3/4"		90-100	Optimum Moisture (%)		Nearest Whole Number
1/2"		-	RAP Blend % Oil Content		1.5% Maximum
3/8"		-	Percent Wear		45% Maximum
No. 4		35-65	Fractured Faces (%)		70% Maximum
No. 8		-	Plasticity Index		* Maximum From Table 3
No. 16		15-40	Liquid Limit		35% Maximum
No. 30		-	Resistance ( R value)		78 Minimum
No. 50		-	Sp. Gravity of +3/4"		-
No. 100		-	Total Available Water Soluble Sodium Sulfates		0.3 Maximum
No. 200		2-10	USCS Classification		-
* Section 704.03.01 Standard Specifications			<u>Visual Description</u> (Color)		-

**A graph of the Moisture-Density Relationship must be attached**

Submitted By: \_\_\_\_\_ P.E. Stamp: \_\_\_\_\_  
(Signature)

\_\_\_\_\_  
(Print Name)

\_\_\_\_\_  
(Title)